

GFRP WRAPPED HIGH STRENGTH CONCRETE SHORT CIRCULAR COLUMNS

Anoop Albert¹ and N Sakthieswaran²

¹M.E student, Regional centre of Anna University, Tirunelveli.

²Assistant Professor, Regional centre of Anna University, Tirunelveli.

ABSTRACT: A major part of the civil engineering infrastructure will need significant repairs. The innovative rehabilitation and strengthening methods for reinforced concrete structures, especially with composite materials, has taken a large portion of the research work in the field of repair and restoration of structural elements. Also, some of these techniques were used to strengthen columns by confinement with composite enclosure. This paper investigates the strengthening of High Strength Concrete short circular columns using Glass Fiber Reinforced Polymer [GFRP] fabric. The main variables of the work are the slenderness ratio of the columns and the number of layers of GFRP wrapping. Column specimens of three different slenderness ratios [3, 6 and 9] each wrapped with 3 and 4 layers of GFRP fabric was considered for the study. Another set of unwrapped columns serves as the reference. The diameter of the columns is 150 mm. The columns were tested under uni-axial compressive loading until failure. The test result shows that the load carrying capacity of the columns improved with the increasing slenderness ratio and number of layers of GFRP wrapping.

Keywords: GFRP wrapping, slenderness ratio, confinement

INTRODUCTION

Fiber reinforced plastic [FRP] materials are very often utilized in the form of bars, strips or sheets for retrofitting or strengthening of reinforced concrete members subjected mainly to axial or flexural and shear forces. In the case of RC columns the most common use of these materials is based on external wrapping with flexible layers of FRP sheets. The connection of FRP sheets to reinforced concrete members proves to be effective with epoxy resin and adopting adequate over-lap length obtained by wrapping the FRP on itself. This reinforcing technique can determine enhancements of strength and strain capacities due to the lateral restraint (confinement effect) exercised by FRP

[1]. Focusing attention on the behavior of compression members, the main parameters considered in researches are the type of FRP material (carbon, glass, aramid, etc.) and its manufacture (unidirectional or bi-directional wraps), the shape of the transverse cross-section of the members, the dimensions and the shape of specimens, the strength of concrete, and the types and percentages of steel reinforcements [2].

An FRP system wrapped around a column provides passive reinforcement to the column [3]. However, once the concrete dilates and begins to crack and weaken, the FRP reinforcement provides confinement for the concrete. The enveloping wrap provides more confinement than a longitudinal or spirally wrapped steel rebar. It is important to note that external FRP reinforcement should only be utilized as tensile reinforcement since the compressive properties of the same are not reliable [4]. Shape of cross section, corner radius, grade of concrete, FRP volumetric ratio are some of the important factors that affect the confinement effectiveness of FRP wraps. In case of circular columns, the whole cross sectional area is effectively confined because the confining pressure is uniformly distributed along the perimeter [5-7]. As the thickness of the confinement increases, the integrity of the system improves leading to higher strength of the specimens, with the wrap having no damage even after the failure of the column [8-9]. Similar studies were also conducted on columns made of plain cement concrete, i.e., the internal steel reinforcement was replaced by external confinement using Glass-FRP. The confined columns exhibited improved strength and ductility compared to the unconfined ones [10]. Confinement modulus and confinement strength of FRP are considered to be the two main factors affecting the performances of FRP-confined concrete columns [11].

When exposed to outdoor conditions, GFRP sheets gained strength due to the increase in the strength of epoxy due to cross-linking of bonds in it [12]. The effects of environmental

conditioning on confinement of concrete with GFRP jackets are much less severe than those found on the mechanical properties of the GFRP material alone [13]. When the FRP-wrapped concrete is subjected to an axial compression loading, the concrete core expands laterally. This expansion is resisted by the FRP wrap, and therefore the concrete core is changed to a three dimensional compressive stress state. In this state, performance of the concrete core is significantly influenced by the confinement pressure [14]. Eccentricity of loading reduces the load carrying capacity of the columns [15].

Carbon FRP confined columns failed explosively, while Glass FRP confined specimens showed adequate warning in the form of white patches on FRP surface at the time of initiation of failure [16]. Previous researches [17] show that the use of FRP confinement changed the failure mode, from brittle shear failure to ductile bending failure, for completely wrapped columns. Also ductility was increased due to transfer to the embeddings, creating a hinge by advanced yielding of longitudinal reinforcements. Failure of FRP confined concrete is indeed initiated by tensile rupture of the FRP wraps at strains close to [or exceeding] the coupon failure strain [18]. Corrosion products occupy greater volume than the original material inducing expansive forces in concrete which leads to the spalling of cover reinforcement degradation [19].

Combination of FRP jacketing and Near Surface Mounted [NSM] FRP rods improves the flexural capacity of damaged as well as undamaged columns. FRP jacketing is provided after embedding the FRP rods in grooves made close to the surface [20]. Even though the initial stiffness of specimens repaired with FRP is lower than that of the original specimens, the rate of deterioration of stiffness of the former under large reversed cyclic loading was lower than the latter ones [21]. FRP increases the compressive strength of short columns to an extent between 1.5 and 3 times of the ordinary columns. But, with increasing slenderness effects can prohibit the column from attaining maximum strength and the column may become susceptible to instability [22]. For any slenderness ratio, the greatest increase in capacity of confined columns is mainly achieved by a two-thirds increase in concrete strength. An increase in concrete strength produced a greater increase in the axial capacity of the column compared to the increase produced in its bending capacity [23-24]. On the other hand, the increase of

fiber thickness and fiber strength produced a greater increase in the bending capacity compared to the increase in the axial capacity [25].

The present work is limited to the study over short columns. Short columns of different heights are considered and the combined effect of slenderness ratio and the confinement provided to them by wrapping with GFRP sheets on the specimens are studied.

2. MATERIALS AND METHODS

An experimental investigation was conducted on 5 sets of column specimens having a diameter of 150 mm with each set comprising of 3 specimens with slenderness ratios of 3, 6 and 9 respectively. Out of these, 4 sets of column specimens were wrapped with Chopped Strand Mat GFRP with different thickness for each slenderness ratio and the remaining one set of specimens serves as the reference. The longitudinal reinforcement consisted of 6 bars of 10 mm diameter and internal ties of 8 mm diameter at a spacing of 150 mm.

2.1 Material Properties

The concrete used for casting the specimens was designed for a compressive strength of 50 MPa with a mix ratio of 1 : 1.35 : 2.19 : 0.35 : 0.8% [Cementitious materials : Fine aggregate : Coarse aggregate : Water : Super plasticizer by weight of binding materials]. The Cementitious materials comprises of Cement [62%], Fly Ash [30%] and Silica Fume [8%]. The mix achieved a characteristic compressive strength of 52 MPa. The reinforcing steel had yield strength of 415 MPa.

2.2 Preparation of Specimens

The moulds used for casting the specimens were made by folding tin sheets into circular shape. Circular clamps having inner diameter of 150 mm were used for firmly holding the circular shape and to provide the required size to the moulds and hence to the specimens. One clamp was provided for every 30 cm [1 ft] height of the mould. In order to ensure adequate cover, cover blocks were placed appropriately and the prepared steel reinforcement cage was placed inside the mould, positioned in such a way that adequate cover was obtained from all sides. The prepared concrete mix was poured into the moulds in layers providing sufficient compaction to the concrete using needle vibrator to avoid honey

combing. The specimens were de-moulded carefully after ensuring complete setting of concrete and cured for 28 days under standard conditions.

2.3 Wrapping with GFRP

The cured specimens were prepared for wrapping with GFRP. The surfaces of the specimens were ground with a high grade grinding wheel to remove all loose and deleterious material from the surface. A jet of compressed air was applied on the surface to blow off any dust and dirt. Then, all surface cavities were filled up with mortar putty to ensure a uniform surface and ensure proper adhesion of FRP to the exterior of concrete. The specimens were wrapped with GFRP fabrics of appropriate fiber type by applying the resin on the surface of the specimens, wrapping them with FRP fabric and applying measured quantities of resin to the application of successive layers of FRP fabric and resin. The wrapped surfaces were gently pressed with

a rubber roller to ensure proper adhesion between the layers and proper distribution of resin.

3. TEST SPECIMENS

The test specimens comprises of 3 sets of column specimens having a diameter of 150 mm with each set comprising of 3 specimens with slenderness ratios of 3, 6 and 9 respectively. Out of these, 2 sets of column specimens were wrapped with Chopped Strand Mat (CSM) GFRP with different thickness for each slenderness ratio and the remaining one set of specimens serves as the reference. The details of the test specimens are given in Table1

4. TEST SET UP

Testing of specimens having heights of 450 mm and 900 mm was carried out in a Universal testing machine of 1000 kN capacity and those of height 1350mm was carried out in a loading frame of 2000KN capacity. The instruments used for testing included deflectometers having a least count of 0.01mm. The load was applied in increments using the loading jack. Axial compression was measured using two dial gauges placed at top and bottom of the specimen

Sl.No.	Specimen Details	Diameter [mm]	Height [mm]	Type of GFRP [mm]	Thickness of GFRP [mm]	Slenderness ratio
1.	C1G0	150	450	-	0	3
2.	C2G3	150	450	CSM	3	3
3.	C3G4	150	450	CSM	4	3
4.	C4G0	150	900	-	0	6
5.	C5G3	150	900	CSM	3	6
6.	C6G4	150	900	CSM	4	6
7.	C7G0	150	1350	-	0	9
8.	C8G3	150	1350	CSM	3	9
9.	C9G4	150	1350	CSM	4	9

Table.1 Details of test specimens



Figure 1. A set of GFRP wrapped specimens



Figure 2. Test set up

5. RESULTS AND DISCUSSIONS

The ultimate loads and deformation on the test specimens are presented in Table 2 and the load deflection curves for all specimens are shown in Figure 3.

Specimen designation	Ultimate load (kN)	Ultimate deflection (mm)
C1G0	144	3.48
C2G3	224	4.28
C3G4	265	5.01
C4G0	373	4.96
C5G3	554	7.66
C6G4	843	9.40
C7G0	501	8.90
C8G3	752	10.42
C9G4	1009	13.40

Table 2. Ultimate Load and deflection details of the tested specimens

5.1 Effect of confinement and slenderness ratio on ultimate load

Slenderness ratio had a notable increase on the ultimate load attained by the confined as well as unconfined column specimens. The ultimate load increased with increase in the slenderness ratio of the specimens. The unconfined specimens with slenderness ratios 6 and 9 showed an increase of 160% and 248% respectively over the specimens with slenderness ratio of 3. Similarly, columns with 3 mm thick GFRP wrap showed an increase of 145% and 236%; and those with 4 mm thick GFRP wrap exhibited 218% and 280% increase in the ultimate load over the specimens with slenderness ratio of 3.

5.2 Effect of confinement and slenderness ratio on deflection

The deflection shown by the specimens increased with increase in the slenderness ratio. Also the GFRP confined specimens allowed for more deflection than the control specimens. This was due to the strength in the confinement provided to the specimens. The failure of the specimens is when the rupture of the FRP confinement occurs.

The load deflection plots of the test specimens are given below:

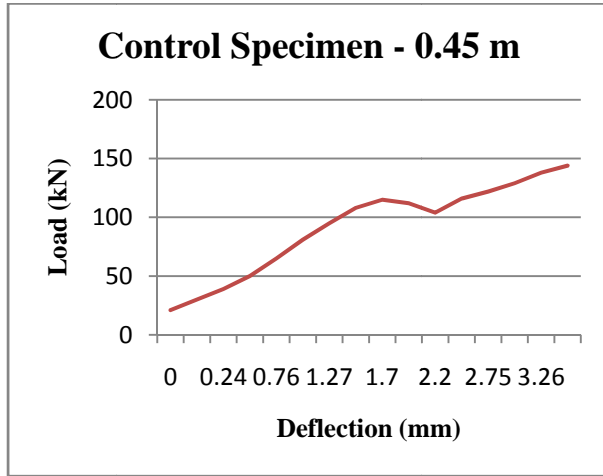


Fig 3a Load deflection plot for unconfined column of height 0.45m

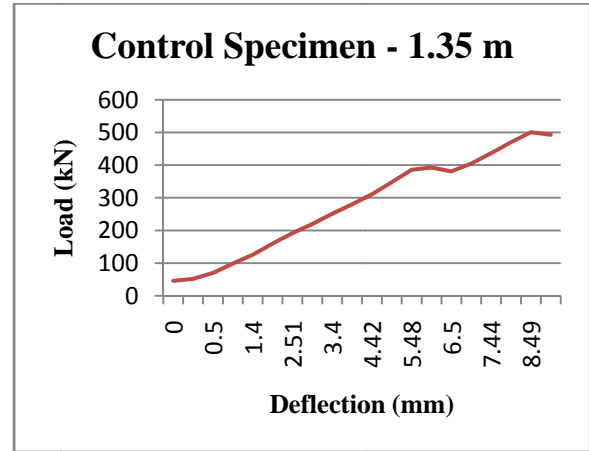


Fig 3e Load deflection plot for unconfined column of height 1.35 m

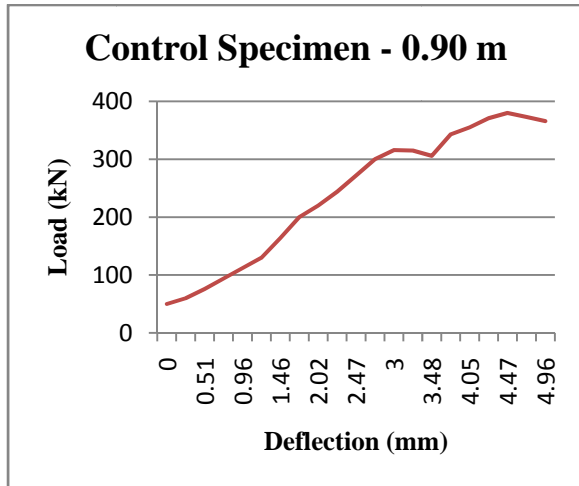


Fig 3c Load deflection plot for unconfined column of height 0.90 m

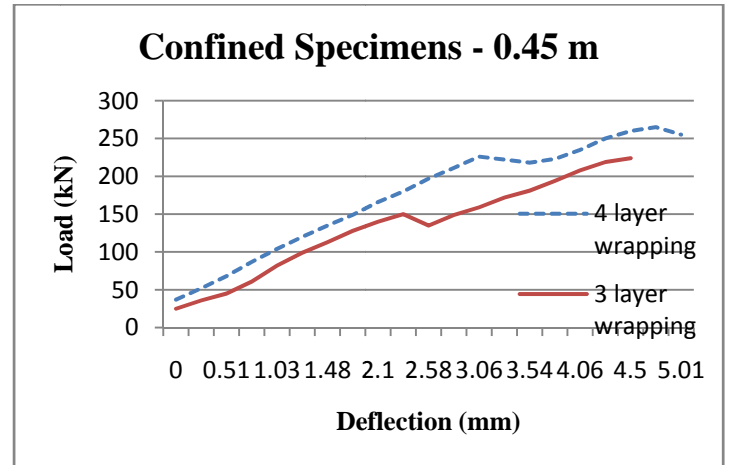


Fig 3b Load deflection plot for confined column of height 0.45m

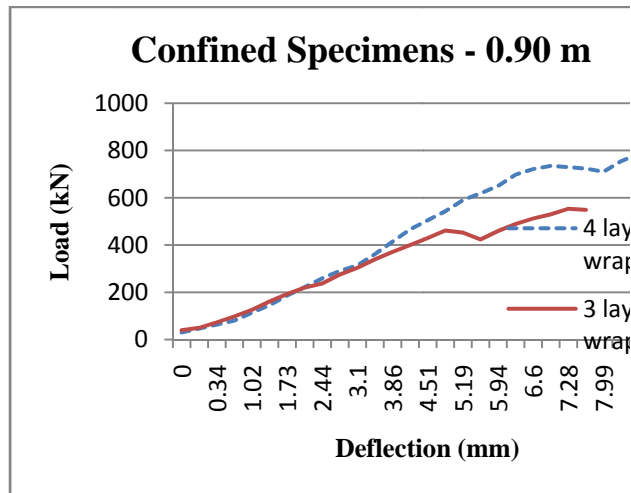


Fig 3d Load deflection plot for confined columns of height 0.9 m

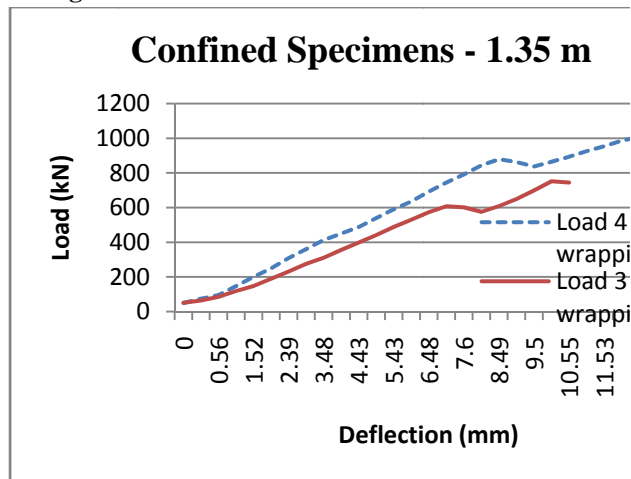


Fig 3f Load deflection plot for confined column of height 1.35 m

5. CONCLUSION

Based on the results obtained through the experimental investigation, the following conclusions were made.

1. As the slenderness ratio increases from 3 to 9, the ultimate load carrying capacity increases by about 250%.
2. When the specimens are confined with GFRP wrapping, the load carrying capacity is again enhanced. As the thickness of the wrap increases from 3mm to 4mm, the load carrying capacity increases by about 280%.

3. Similarly, the deflection on the unconfined specimens increases with the increase in slenderness ratio from 3 to 9.

4. The deflection on the confined specimens also increases with increase in the thickness of the wrap from 3mm to 4mm.

REFERENCES

1. Kamal Nassif Ghali, Sami H Rizkalla, [2009], "FRP Confined Circular Columns Under Small Eccentric Loading", The Arabian Journal Of Science And Engineering No. 1 B, Pg 15 – 26
2. J.Saravanan, K.Suguna, P.N.Raghunath, [2012] "Ductility Behaviour Of High Strength Concrete Columns With GFRP Wraps", Asian Journal Of Civil Engineering, Vol 13, No.6,
3. ACI, 440.2r, [2002], "Guide For The Design And Construction Of Externally Bonded FRP Systems For Strengthening Concrete Structures", Pp. 1-45.
4. Li JH, Hadi MNS, [2004], "External Reinforcement of High Strength Concrete Columns", Elsevier Journal. Of Composite Structures, 65, 279-287.
5. Dr. Abhay Bambole, [2011], "Effect Of Size And Shape On GFRP Composite Wrapped Concrete Columns", Asian Journal Of Civil Engineering, Vol 11, No.5,
6. G.Campione, M.Papia, [2008], "Strength And Strain Enhancements Of Concrete Columns Confined With FRP Sheets", Journal Of Structural Engineering And Mechanics, Vol.18, No.6,
7. Li JH, Hadi MNS, [2003], "Behavior of Externally Confined High Strength Concrete Columns under Eccentric Loading", Journal. Of Composite Structures, 62, 145-153.
8. Mirmiran, A., Shahawy, M. And Beitelman, T. [2001], "Slenderness Limit For Hybrid FRP Concrete Columns", ASCE Journal. Of Compos. for Constr., 5[1], 26-34.
9. Shahawy, M., Mirmiran, A., and Beitelman, T. [2000] "Tests and Modeling of Fiber-Wrapped Concrete Columns." Composites, Part B, 31[6-7], 471-480.
10. M.N.S.Hadi., [2007] "Behaviour of FRP strengthened concrete columns under eccentric compression loading", Composite Structures 77.
11. G. Wu , Z.T. Lu, Z.S. Wu , [2006] "Strength and ductility of concrete cylinders confined with FRP composites", Construction and Building Materials 20, 134-148.
12. A. Mukherjee, S.J. Arwika [2007] "Performance of externally bonded GFRP sheets on concrete in tropical environments Part I: Structural scale tests", Composite Structures 81, 21-32
13. Manuel A.G. Silva, [2007], "Aging of GFRP laminates and confinement of concrete columns", Composite Structures 79, 97-106
14. Parvin. A, Jamwal AS., [2005] Effects of Wrap thickness and Ply configuration on Composite-Confined Concrete Cylinders", Compos Structures; 67[4] : 437-42.
15. Hadi, M. N. S., "Behaviour of FRP Wrapped Normal Strength Concrete Columns under Eccentric Loading", Composite Structures, 72, 2006, pp 503-511.
16. Shahawy, M., Mirmiran, A., and Beitelman, T. [1997] "Behavior of Concrete Columns Confined by Fiber Composites", ASCE Journal of Structural Engineering, 123, 583-590

17. G. Promis, E. Ferrier, P. Hamelin, [2009, “**Effect of External FRP Retrofitting on Reinforced Concrete Short Columns For Seismic Strengthening**”, Composite Structures 88] 367–379
18. Luke A Bisby & Tim J Stratford, [2010], “**The Ultimate Condition of FRP Confined Concrete Columns: New Experimental Observations & Insights**”, CICE 2010 - The 5th International Conference on FRP Composites in Civil Engineering, September 27-29, 2010 Beijing, China
19. S. J. Pantazopoulou, J. F. Bonacci, S. Sheikh, Members, ASCE, M. D. A. Thomas, and N. Hearn, [2001], “**REPAIR OF CORROSION-DAMAGED COLUMNS WITH FRP WRAPS**”, Journal of Composites for Construction, Vol. 5, No. 1, February
20. M.Sarafraz1 and F.Danesh, [2008], “**Flexural Enhancement of RC Columns With FRP**”, The 14th World Conference on Earthquake Engineering October 12-17, 2008, Beijing, China
21. Hamid Saadatmanesh, Mohammad R. Ehsani, and Limin Jin, [1997], “**Repair of Earthquake-Damaged RC Columns with FRP Wraps**”, ACI Structural Journal, V. 94, No. 2, March-April.
22. J.L.Pan, T.Xu, Z.J. Hu, [2007], “**Experimental Investigation of Load Carrying Capacity Of The Slender Reinforced Concrete Columns Wrapped With FRP**”, Construction and Building Materials 21, Pg 1991–1996
23. Manal K. Zaki, [2011], “**Investigation Of FRP Strengthened Circular Columns Under Biaxial Bending**”, Journal of Engineering Structures 33, 1666–1679
24. Hsiao-Lin Chenga, Elisa D. Sotelinob and Wai-Fah Chenc, [2004], “**Sensitivity Study and Design Procedure for FRP Wrapped Reinforced Concrete Circular Columns**”, International Journal of Applied Science and Engineering 2004. 2, 2: 148-162
25. Yung-Chih Wang, K. Hsu, [2008], “**Design of FRP-wrapped reinforced concrete columns for enhancing axial load carrying capacity**”, Journal of Composite Structures 82 [2008] 132–139
26. Priyanka A Jadav, Dilip K Kulkarni, [2012] “**An Experimental Investigation On The Properties Of Concrete Containing Manufactured Sand**”, International Journal Of Advanced Engineering Technology, Vol III, Issue II, April – June 2012, 101 – 104
27. Mahmoud Nili, V.Afroughsabet, [2010], “**Combined Effect Of Silica Fume And Steel Fibers On The Impact Resistance And Mechanical Properties Of Concrete**”, International Journal Of Impact Engineering 37, 879 – 886
28. T. Shanmugapriya and R. N. Uma, [2012], “**Optimization Of Partial Replacement Of M-Sand By Natural Sand In High Performance Concrete With Silica Fume**”, International Journal of Engineering Sciences & Emerging Technologies, June 2012, Volume 2, Issue 2, pp: 73-80