

EFFECTS OF GGBFS AS POZZOLANIC MATERIAL WITH GLASS FIBER ON MECHANICAL PROPERTIES OF CONCRETE

Prof. Pankaj B. Autade¹, Anil B Wakankar²

¹Asst.Prof. Department of Civil Engineering, PDVVP College of Engineering, Ahmednagar, India

²Anil B Wakankar, M E Scholar PDVVP College of Engineering, Ahmednagar, India

ABSTRACT

From last many decades, usage of concrete has increased on large scale all over the world. Concrete ingredients used are becoming more costly day by day and also demand for the same is increasing widely all over. One of the main ingredients is cement, while production of cement CO₂ is emitted out which is responsible for global warming. Replacement of cement by a pozzalanic material named Ground Granulated Blast Furnace Slag, which is waste product of steel manufacturing industries. Glass fiber of 12mm size was also added to increase both compressive and tensile strength of concrete. In present paper focuses on using GGBFS as replacement material to cement in different percentage 0%, 20%, 30% and 40% by weight of cement and Glass Fiber is also added to concrete in different proportion 0%, 0.03% and 0.06% by total volume. Twelve mixes of concrete with GGBFS and Glass Fiber were studied with w/c ratio 0.39 and Superplasticizer named CONPAST SP-430. Combinable effect of GGBFS and Glass Fiber is best for 30% GGBFS and 0.06% Glass Fiber as we know that concrete starts bleeding above 30% replacement by GGBFS and Glass Fiber controls the bleeding of concrete.

Keywords: Ground Granulated Blast Furnace Slag (GGBFS) and Glass Fiber (GF)

1. Introduction

Concrete is one of the most widely used materials for Civil engineering structures due to its inherent properties. Concrete is mixture of cement, fine aggregate, coarse aggregate and water. Cement is the second largest material

used in world after water. During production of cement there is CO₂ emitted out from industry. Producing one ton of Ordinary Portland Cement releases about one ton of CO₂ green house gas into atmosphere and as a result of this production 1.6 billion tons of CO₂ is released every year. This released CO₂ is estimated to be 7% of the CO₂ production worldwide (Ozkan Senul and Mehmet Ali Tasdemir 2009) and CO₂ have many dangerous side effect like global warming. Long studies over years have given that there is no second alternative for replacing cement totally. There is also another problem regarding consumption of lime on large scale all over the world which is extinguishing. One of the waste materials is Ground Granulated Blast Furnace Slag. It is the material confirming up to the mark similar chemical properties as cement do. GGBFS based concrete gives us two in one advantages like as it replaces the cement which has many more drawbacks and also utilizes waste from steel industry. Whatever the facilities provided related to construction in the city should have good durability. So to improve the strength of concrete Glass Fiber is also introduced in concrete. Ground Granulated Blast furnace Slag (GGBFS) is a non-metallic product, consisting of silicates and alumino silicates of calcium and other bases, developed in a molten condition simultaneously with iron in a blast furnace. From structural point of view, GGBS replacement enhances lower heat of hydration, higher durability and higher resistance to sulphate and chloride attack when compared with normal ordinary concrete. On the other hand, it also contributes to environmental

protection because it minimizes the use of

2. Experimental Investigation

2.1. Materials used

Cement

Ordinary Portland cement, 53 Grade conforming to IS:8112-1989[4]. The specific gravity of cement was 3.15. Fine aggregate Locally available river sand conforming to Grading zone II of IS: 383 1970[5]. Its specific gravity was 2.6. Coarse aggregate Locally available crushed basalt aggregate both 20mm and 10mm size was used in 60:40 proportion of total aggregate used as per IS: 383 – 1970

Ground Granulated Blast Slag (GGBS)

Ground granulated blast furnace slag obtained from Sona Alloys, C-1, MIDC, Lonand, Satara. Ground granulated blast-furnace slag is the granular material formed when molten iron blast furnace slag is rapidly chilled (quenched) by immersion in water. It is a granular product with very limited crystal formation, is highly cementitious in nature and, ground to cement fineness, and hydrates like Portland cement. Properties of GGBFS are as shown below:

Calcium Oxide(CaO)	40-52
Silicon Dioxide(SiO ₂)	10-19
Iron Oxide(FeO)	10-40
Manganese Oxide(MnO)	5-8
Magnesium Oxide(MgO)	5-10
Aluminium Oxide(Al ₂ O ₃)	1-3
Phosphorous Pent Oxide(P ₂ O ₅)	0.5-1
Sulphur(S)	< 0.1
Metallic Fe	0.5-10

Super Plasticizer

A commercially available sulphonated naphthalene formaldehyde based super plasticizer (CONPLAST SP 430) was used as chemical admixture to enhance the workability of the concrete.

Glass fiber (GF)

cement during the production of concrete.

The glass fibers used in concrete suppressed the localization of micro cracks in to macro cracks hence tensile strength increase. It improves durability of concrete by increasing the strength of concrete. The Glass Fibers are of Cem-FIL Anti - Crack HD are used for experimentation work.

Table No.3.8 Physical Properties of Glass Fiber

Sr.No.	Property	Value
1	Diameter	14 microns
2	Length of fiber	12mm
3	Appearance	Shiny hair like
4	Aspect Ratio	857:1
5	Shape of Fiber	Straight
6	Tensile Strength	1700 MPa
7	Modulus of Elasticity	72 GPa
8	Specific Gravity	2.68
9	Number of Fiber per Kg	212 million

3. Mix Proportion and Mix details

In this investigation IS 10262-2009 is considered for Mix Design and M₃₀ Grade is used. On the basis of trial and error following mix were used:

Water	Cement	CA		FA
		20mm	10mm	
177.055lit	405 Kg/m ³	664 Kg/m ³	443 Kg/m ³	824 Kg/m ³
0.39	1	1.639	1.093	2.034

For 1 m³ = 2494 Kg /m³

4. Test Specimens and Test procedure

The ingredients of concrete are weighing properly and mixed thoroughly to get consistency to the concrete considering the mix proportion. Superplasticizer is added to water and then mixed to the dry mix. Specimens were compacted on table vibrator and tapping rod to get a homogeneous mixture. Specimens used are cubes, cylinders and beams specially prepared to measure compressive

strength, splitting tensile strength and flexural strength respectively. Dimensions of each test specimen are as under:

Cube: 150mm×150mm×150mm
 Cylinder: 150mm in diameter and 300mm long
 Beam: 100mm×100mm×500mm

5. TESTS AND RESULT ANALYSIS


5.1. Compressive Strength Results

The compressive strength of concrete was determined at the age of 3 days, 7 days and 28 days. The specimens were cast and tested as per IS: 516-1959.


Table No. 1 Compressive Strength of Concrete

Trial No.	GGBFS (%)	Glass Fiber (%)	Compressive Strength			% Variation in Compressive Strength over Control Concrete		
			3 Days	7 Days	28 Days	3 Days	7 Days	28 Days
T1	0	0.0	21.333	24.296	37.78	0	0	0
T2		0.03	29.185	32.899	43.11	36.806	35.368	14.108
T3		0.06	25.778	27.704	40.74	20.836	14.027	7.835
T4	20	0.0	25.703	28.889	41.93	20.485	18.904	10.985
T5		0.03	26.815	28	40.444	25.697	15.245	7.051
T6		0.06	22.263	25.481	40	7.641	4.877	5.876
T7	30	0.0	24.593	26.444	40.444	15.281	8.841	7.041
T8		0.03	23.259	24	38.81	9.028	-1.218	2.726
T9		0.06	23.37	26.444	40.15	9.549	8.841	6.273
T10	40	0.0	19.852	25.333	31.778	-6.492	4.268	-15.887
T11		0.03	17.778	22.37	30.444	-16.664	-7.927	-19.418
T12		0.06	17.185	20.444	26.444	-19.444	-15.854	-30.005

Graph No. 1 GGBFS Vs Compressive Strength when 0.0 % Glass Fiber

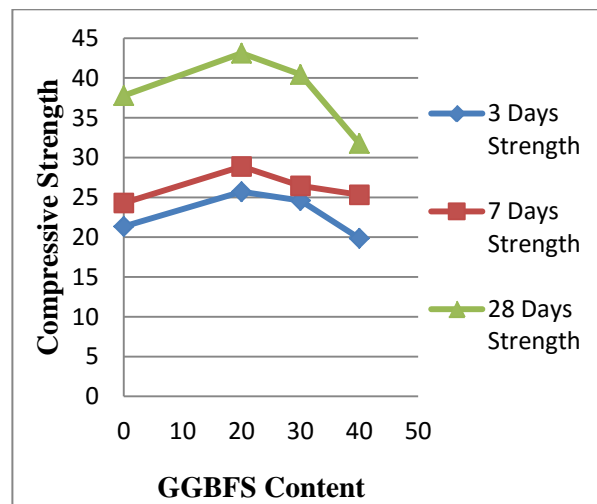

Graph No. 2 GGBFS Vs Compressive Strength when 0.03 % Glass Fiber

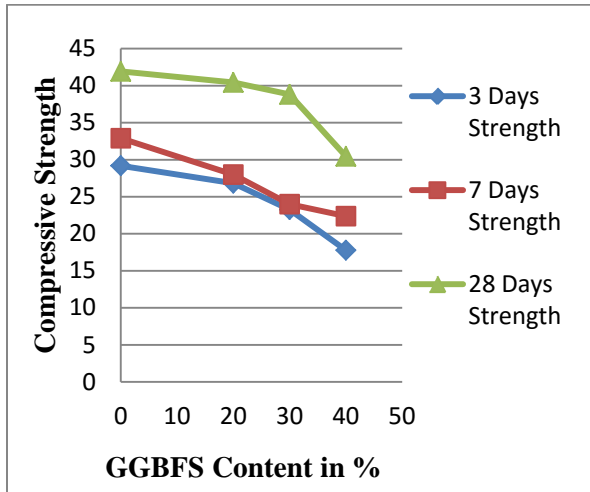


Graph No. 3 GGBFS Vs Compressive Strength when 0.06 % Glass Fiber


Compressive Strength increases with GGBFS addition for 20% up to 41.93N/mm² which is more than the control concrete. GGBFS also increase strength up to 30% replacement but there after there is reduction in Strength. GGBFS and Glass Fiber together also give increase in compressive strength than the controlled concrete but they more compressive strength individually. If we check the graph 3 we can get to know that with 30% GGBFS and 0.06% Glass Fiber gives more Strength than 20% GGBFS and 0.06% and all other combinations in the graph.

5.2. Split Tensile Strength Results

The splitting tensile strength of concrete cylinder was determined based on 516-1959. The load shall

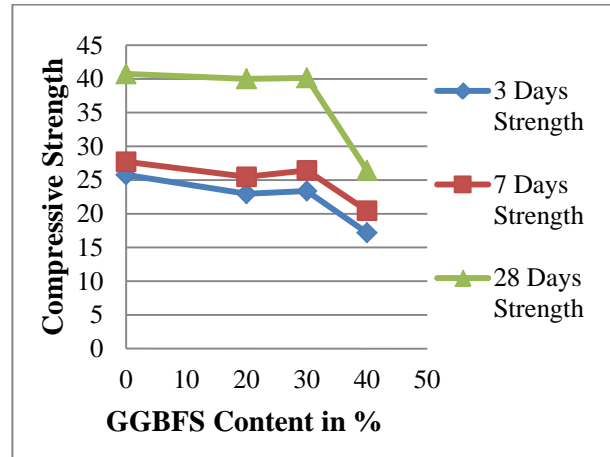

Graph No.4 GGBFS Vs Split Tensile Strength

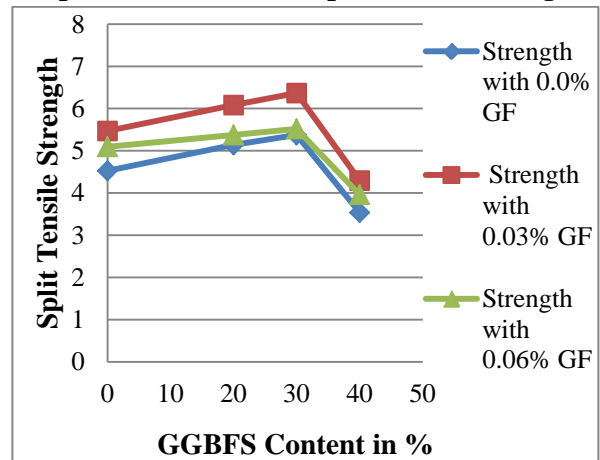

be applied nominal rate within the range 1.2 N/ (mm²/min) to 2.4 N/ (mm²/min). Load is applied until the specimen fails, along the vertical diameter.

Split tensile strength increases between range of 20% to 30% of GGBFS addition and gives more strength for 0.03% addition of Glass Fiber. Here split tensile strength was highest at 30% GGBFS content and 0.03% Glass Fiber content. All the results for split tensile strength are greater than controlled concrete except 40% replacement of GGBFS do not prove better.

Table No. 2 Splitting Tensile Strength of Concrete

Trial No.	GGBFS (%)	GF (%)	Splitting Tensile Strength in N/mm ²	% Variation in Splitting Tensile Strength
T1	0	0.0	4.527	0.00
T2		0.03	5.471	20.842
T3		0.06	5.329	17.717
T4	20	0.0	5.140	13.550

5.3. Flexural Strength Test on Beams

The results of flexural strength are presented in table below:

Table No. 4.11 Flexural Strength of Concrete


Trial No.	GF (%)	GGBFS (%)	Flexural Strength in (N/mm ²)	% Variation in Flexural Strength
T1	0.0	0	10.91	0
T4		20	7.85	-28.06
T7		30	13.21	21.07
T10		40	9.675	-11.34
T2	0.03	0	12.5	14.54
T5		20	8.3	-23.94
T8		30	14.3	31.04
T11	0.06	40	11.175	2.4
T3		0	13.25	21.42
T6		20	9.375	-14.08
T9		30	14.775	35.39
T12	40	40	12.24	12.16

T5		0.03	6.084	34.385
T6		0.06	5.093	12.508
T7	30	0.0	5.376	18.508
T8		0.03	6.367	40.635
T9		0.06	5.329	17.717
T10	40	0.0	3.537	-21.869
T11		0.03	3.844	-15.098
T12		0.06	4.716	4.174


Discussion

Highest flexural strength was achieved at combination 30%GGBFS and 0.06%GF i.e. trial number T9. Flexural strength is reduced at 20% addition of GF. Results in the Graph 4.10 shows that Flexural strength for 0%, 20%, 30% and 40% GGBFS increases with increase in GF content.

Graph No. 4.9 %GGBFS Vs Flexural Strength

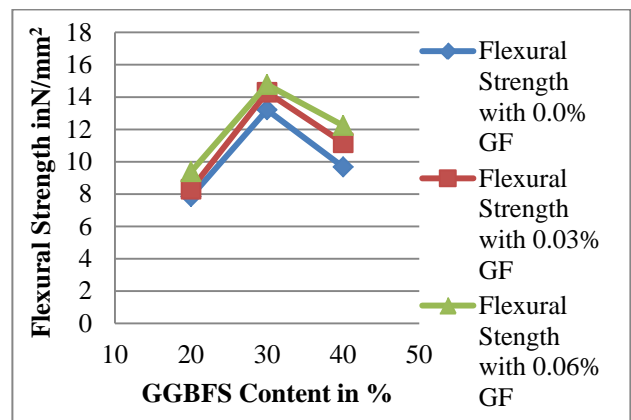

Graph No. 4.10 %GF Vs Flexural Strength

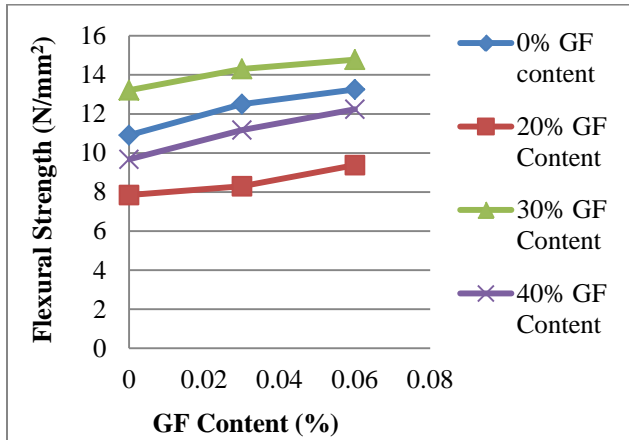

6. CONCLUSION

- It is observed that the GGBFS based Glass Fiber can have higher strengths.
- Compressive Strength is highest at the T2 trial means with 0.03% of Glass Fiber.
- Splitting Tensile Strength is highest at the T8 trial means with 30% GGBFS and 0.06% Glass Fiber.

REFERENCES

- Awasare Vinayak, Prof. M.V. Naendra, "Analysis Of Strength Characteristics Of GGBS Concrete" International Journal Advance Engg Tech, Vol. V, Issue II, (April-June,2014), pp 82-84
- Atwell J.S.F., Some Properties of Grind Granulated Blast Slag and Cement. Proc. Instn. Civ. Engrs, Part 2, 57, June, pp 233-250
- Boukendakdji Othmane, El-Hadj Kadri, Said Kenai, "Effects of granulated blast furnace slag and superplasticizer type on the fresh properties and compressive strength of self-compacting concrete" Cement & Concrete Composites 34 (2012), pp 583–590
- Bamforth J.J., In-Situ Measurement of the Effect of Partial Portland Cement Replacement Using either Fly Ash or Ground Granulated Blast Furnace Slag on the Performance of Mass Concrete. Proc., Instn Civ Engrs, Part 2, 57, June, pp 777-800.
- Caijun Shi and Jueshi Qian, "High performance cementing materials from industrial slag's", Resources' Conservation & Recycling, Vol. 29, 2000, pp 195-207
- Chandramouli K., Srinivasa Rao P., Pannirselvam N., Seshadri Sekhar T. and Sravana P., "Strength Properties Of Glass Fibre Concrete" ARPN Journal of Engineering and Applied Sciences, VOL. 5, NO. 4, APRIL 2010, pp 1-6
- D.V.S.P. Rajesh, A. Narender Reddy, U. Venkata Tilak, M. Raghavendra, "Performance Of Alkali Activated Slag With Various Alkali Activators" International Journal of Innovative Research in Science, Engg and Technology, Vol. 2, Issue 2, Feb 2013, pp 378-386
- Duos C., and Eggers J, Evaluation of Ground Granulated Blast Furnace Slag in Concrete (Grade 120). Rpt. No. FHWA/LA-99/336
- Deshmukh S.H. , Bhusari J. P , Zende A. M., "Effect of Glass Fibers on Ordinary Portland cement Concrete" IOSR Journal of Engg, Vol. 2(6), June. 2012, pp 1308-1312
- Dubey Atul, Dr. Chandak R., Yadav R.K., "Effect of blast furnace slag powder on compressive strength of concrete" International Journal of Scientific & Engineering Research Vol 3, Issue 8, August-2012, pp 1-4

- Based on the results the compressive and split tensile strengths are increased as the percentage of GGBFS increased.
- Combinable effect of GGBFS and Glass Fiber is also good for 30% GGBFS and 0.06% Glass Fiber as we know that concrete starts bleeding above 30% replacement by GGBFS and Glass Fiber controls the bleeding of concrete.
- Higher strength development is due to filler effect of GGBS and properties of glass fibers.
- As split tensile strength increases, formation of micro-cracks are avoided which is due to Glass Fiber addition.
- From the experimental results 20-30% of cement can be replaced with GGBFS.
- The addition of super plasticizer also tends to reduce strength of concrete due to the chemical action between the super plasticizer and GGBS.
- The flexural strength increases with increase in Glass Fiber content.
- Results shows that the flexural strength increases for 0%, 30% and 40% GGBFS content, with increase in GF content.

11. Feldman R.F., Significance of Porosity Measurements on Blended Cement Performance. American Concrete Institute, Farmington Hills, 1983, pp 415-433.
12. Gadge A Nikhil., Prof. S. S. Vidhale, "Mix Design of Fiber Reinforced Concrete Using Slag & Steel Fiber" International Journal of Modern Engineering Research, Vol. 3, Issue. 6, Nov - Dec. 2013, pp 3863-3871
13. Gadpalliwar Sonali K., R. S. Deotale and Abhijeet R. Narde, "To Study the Partial Replacement of Cement by GGBS & RHA and Natural Sand by Quarry Sand In Concrete" Journal of Mechanical and Civil Engineering, Volume11, Issue 2 Ver. II (Mar- Apr. 2014), pp 69-77
14. Gengying Li, Xiaohua Zhao, "Properties of concrete incorporating fly ash and ground granulated blast-furnace slag" Cement & Concrete Composites 25 (2003), pp 293–299
15. Higgins D, Briefing: GGBFS and Sustainability. Institution of Civil Engineers Construction Materials, Issue CM3, Aug 2007, pp 99-101
16. I. Papayianni , G. Tsohos, N. Oikonomou, P. Mavria, "Influence of superplasticizer type and mix design parameters on the performance of them in concrete mixtures", Cement & Concrete Composite, Vol. 27, 2005, pp 217-222
17. Janusz Potrzebowski, "The splitting test applied to steel fiber reinforced concrete", The International Journal of Cement Composites and Lightweight Concrete, Vol. 5, No. 1, February 1983
18. Juan Lizarazo-Marriaga, Peter Claisse and Eshmaiel Ganjian, "Effect of Steel Slag and Portland Cement in the Rate of Hydration and Strength of Blast Furnace Slag Pastes" Journal Of Materials In Civil Engineering © Asce / February 2011, pp 153-160
19. K Ganesh Babu and V. Sree Rama Kumar, "Efficiency of GGBS in Concrete", Cement and Concrete Research , Vol. 30, 2000, pp 1031-1036
20. Kumar P. and Kaushik S.K., "Some trends in the use of concrete: Indian Scenario", The Indian Concrete Journal, Dec 2003, pp 1503-1508
21. M. Collepardi, "Admixtures used to enhance placing characteristics of concrete", Cement & Concrete Composite, Vol. 20, 1998, pp 103-112
22. Mirza Faiz , Parviz Soroushian, "Effects of alkali-resistant glass fiber reinforcement on crack and temperature resistance of lightweight concrete" Cement & Concrete Composites 24 (2002), pp 223–227
23. Ozkan Sengul, Mehmet Ali Tasdemir, "Compressive Strength and Rapid Chloride Permeability of Concretes with Ground Fly Ash and Slag" Journal Of Materials In Civil Engineering © Asce / September (2009), pp 494-501
24. Rashad Alaa M., Hosam H. Seleem, and Amr F. Shaheen, "Effect of Silica Fume and Slag on Compressive Strength and Abrasion Resistance of HVFA Concrete" International Journal of Concrete Structures and Materials, Vol.8, No.1, March 2014, pp 69–81.
25. Scott A. and Alexander M.G. " The influence of Binder Type, Cracking and Cover on Corrosion Rates of Steel in Chloride Contaminated Concrete ." Magazine of Concrete Research, September 2007, 59, No.7, pp 495-505.
26. S. Arivalagan, "Sustainable Studies on Concrete with GGBS As a Replacement Material in Cement". Jordan Journal of Civil Engg, Vol 8, No. 3, 2014, pp 263-270
27. Tassew S.T., A.S. Lubell, "Mechanical properties of glass fiber reinforced ceramic concrete" Construction and Building Materials 51 (2014), pp 215–224
28. Tam C.T., LooY.H.H., "Adiabatic Temperature Rise in Concrete with and without GGBFS." American Concrete Ins, Farmington Hills, Mich., 1983, pp 649-662
29. Zollo Ronald F., "Fiber-reinforced Concrete: an Overview after 30 Years of Development", Cement & Concrete Composite, Vol. 19, 1997, pp 107-122